

Production of Micro- and Nanoporous, Superhydrophobic layers from Sol-Gels



Neil J. Shirtcliffe, Paul Roach, Glen McHale, Michael Newton, Carole C. Perry

Silicate Sol Gels



Sol-Gel= preparation of oxide materials from solution

Usually organosilicon compounds hydrolysed to form intermediates


Partially & fully hydrolysed silicates can link together

Solvent creates porous structure unless complete separation occurs



Hydroxide and organic groups usually present until thermally treated

Mechanism


Acid Hydrolysis

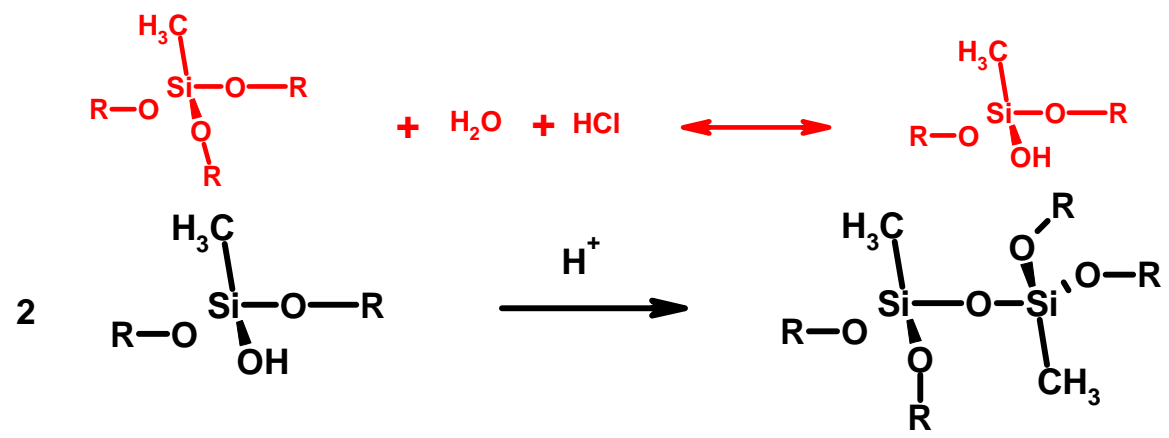


Base Catalysed Gelation

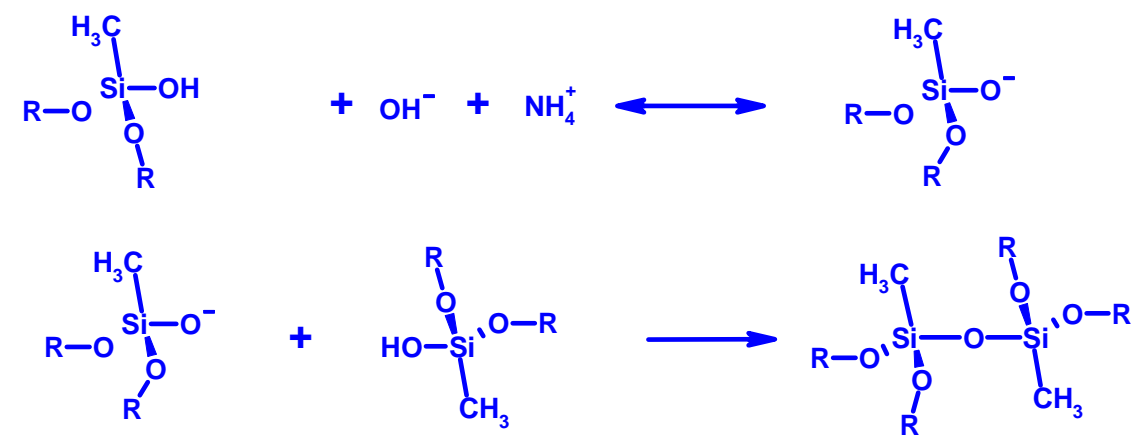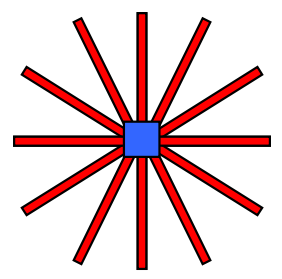

Sol-Gel Phase Separation

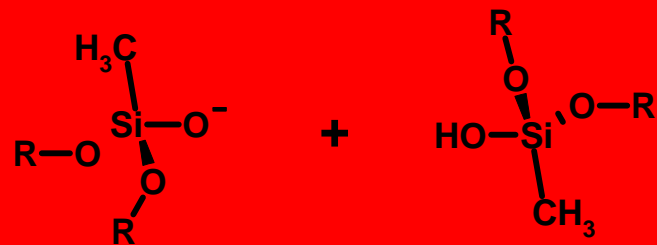


Polar

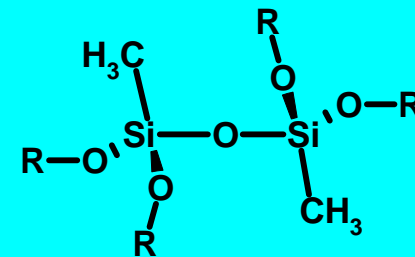


Less Polar

As the chains grow they become more hydrophobic and eventually phase separate to form a bicontinuous structure


Bi-continuous Structure

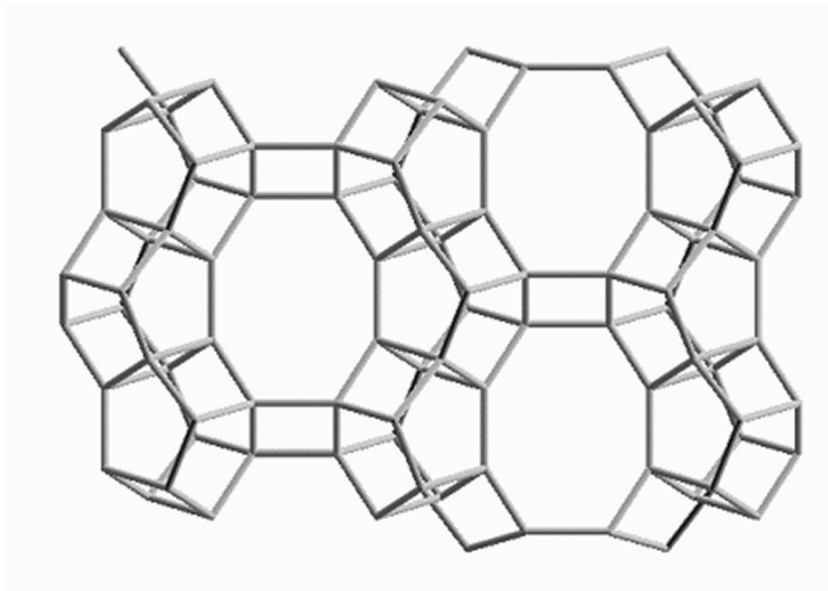

M. Stockenhueber

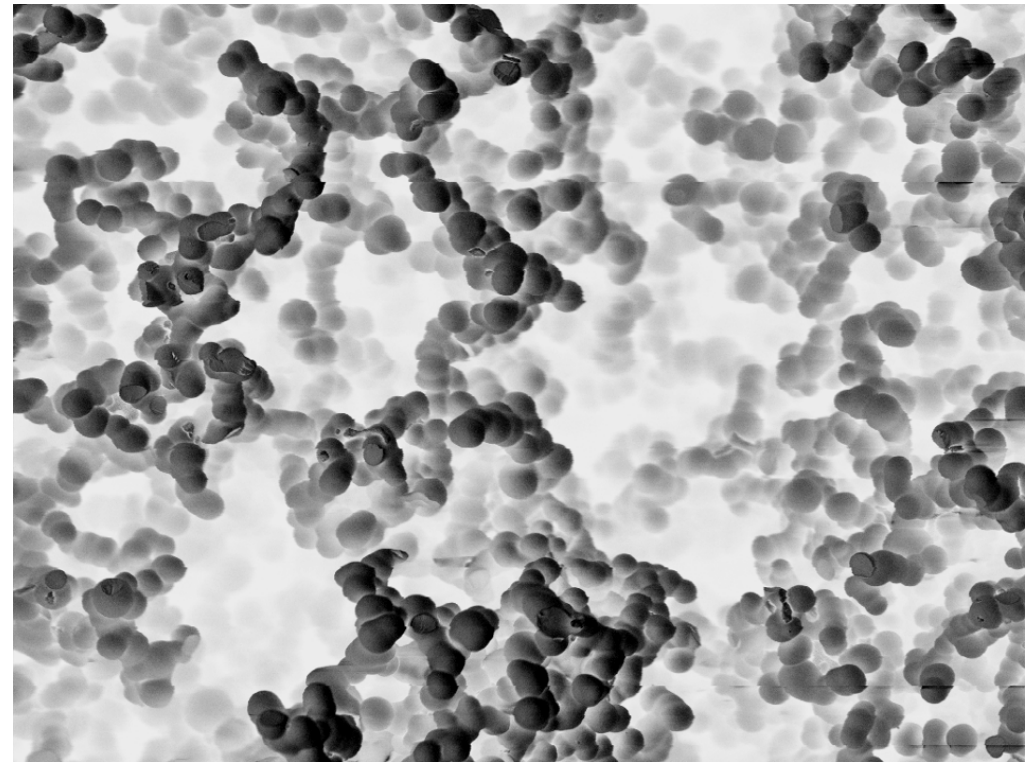

Shrinkage

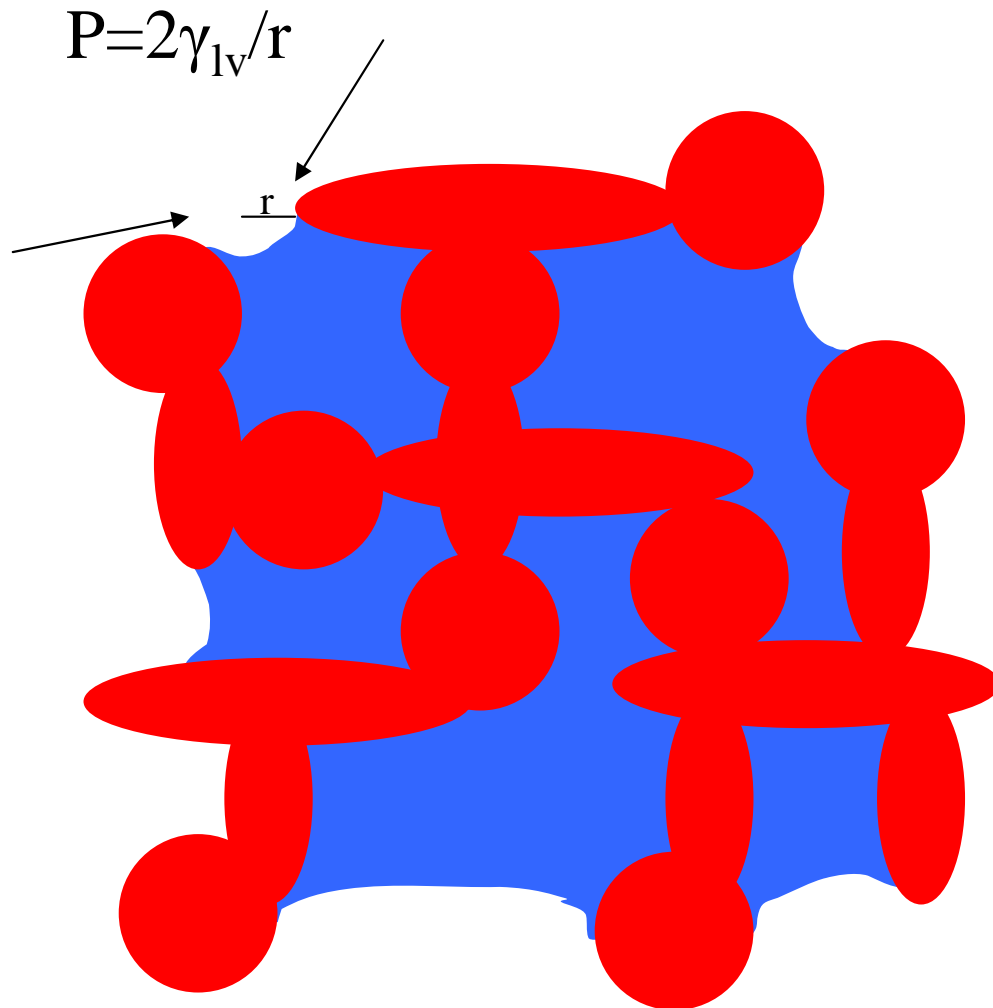

Shrinkage caused by surface tension of drying solvent, varies with pore size. Means that total pore volume decreases with pore size.

Can be overcome by supercritical drying, this is technically easy but takes time=money

Size Of Domains



- Rate of phase separation

- Polarity of solvent
- Starting material
- Temperature




- Rate of hardening

- Starting material
- Time in acid
- Temperature

- Shrinkage

- Surface tension
- Contact angle of solvent “r”
- Pore Size “r”
- Strength
- (Temperature/pH=coarsening)


Super-hydrophobicity

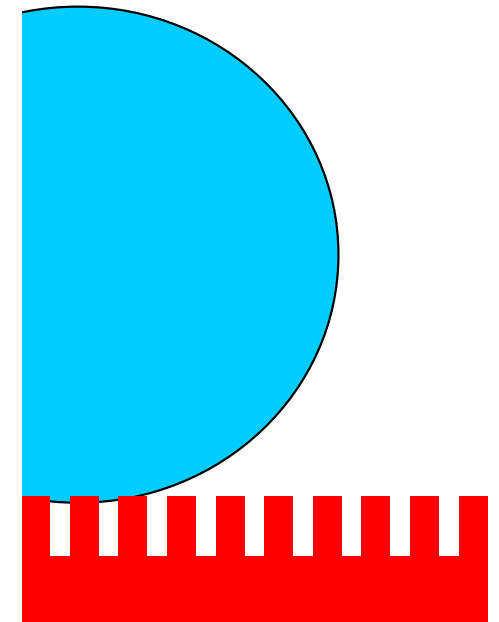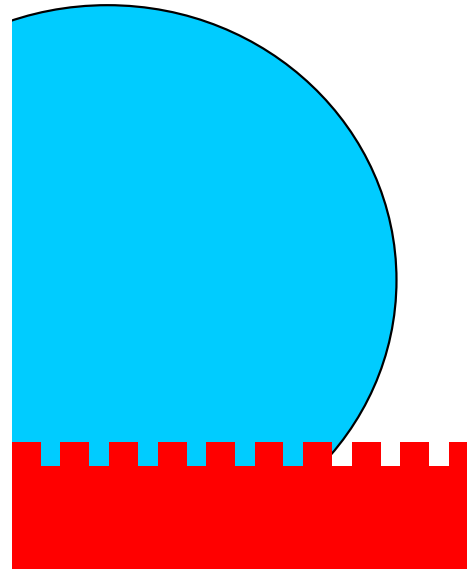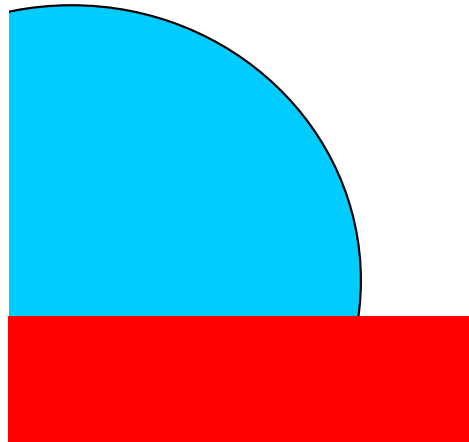



Max. Angle 120°

Super-hydrophobicity

Flat Teflon



Lotus Leaf
Barthlott &
Neinhuis

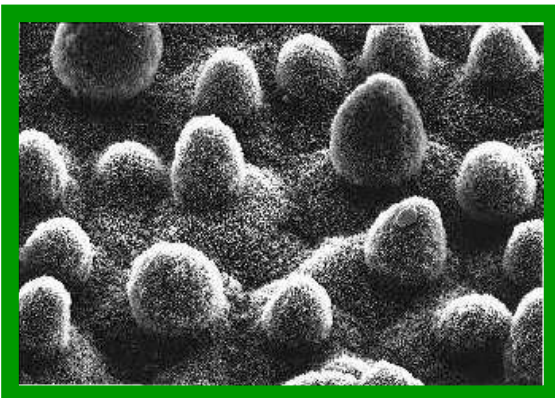



Sol-Gel Foams





Advancing and receding contact angles of drops of water on organo-silica flat surfaces and foams. Foam 1- MTEOS sol-gel produced using 1.1 M ammonia: Foam 2- sol-gel produced using MTEOS and 2.2 M ammonia.

Materials			Advancing Angle $\Theta/^\circ$	Receding Angle $\Theta/^\circ$	Hysteresis $\Delta\Theta/^\circ$
Sample	Temp./ $^\circ$ C	Post treatment			
Flat	300	None	107	87	20
Flat	400	None	90	69	21
Flat	500	None	81	67	14
Flat	550	None	54	31	12
Foam1	300	None	153	137	16
Foam1	300	Abraded	156	152	4
Foam2	300	None	155	149	6
Foam1	400	None	Absorbed	Absorbed	-

Effect of Heating

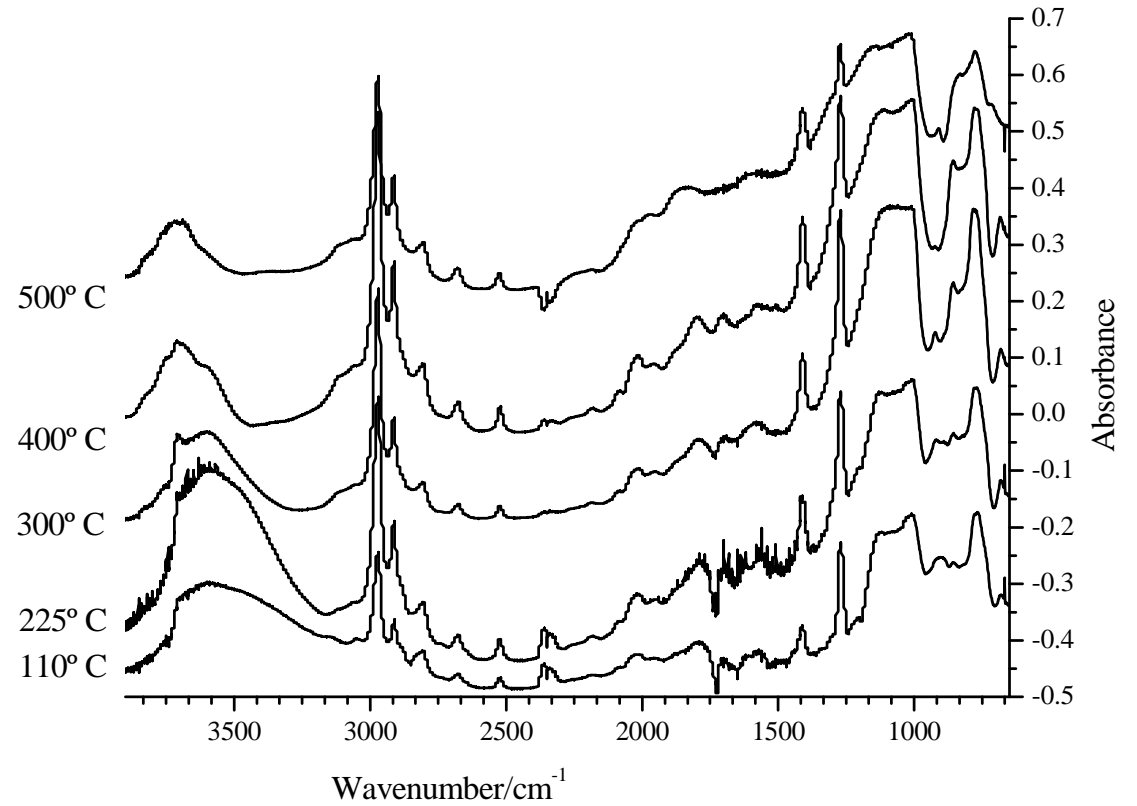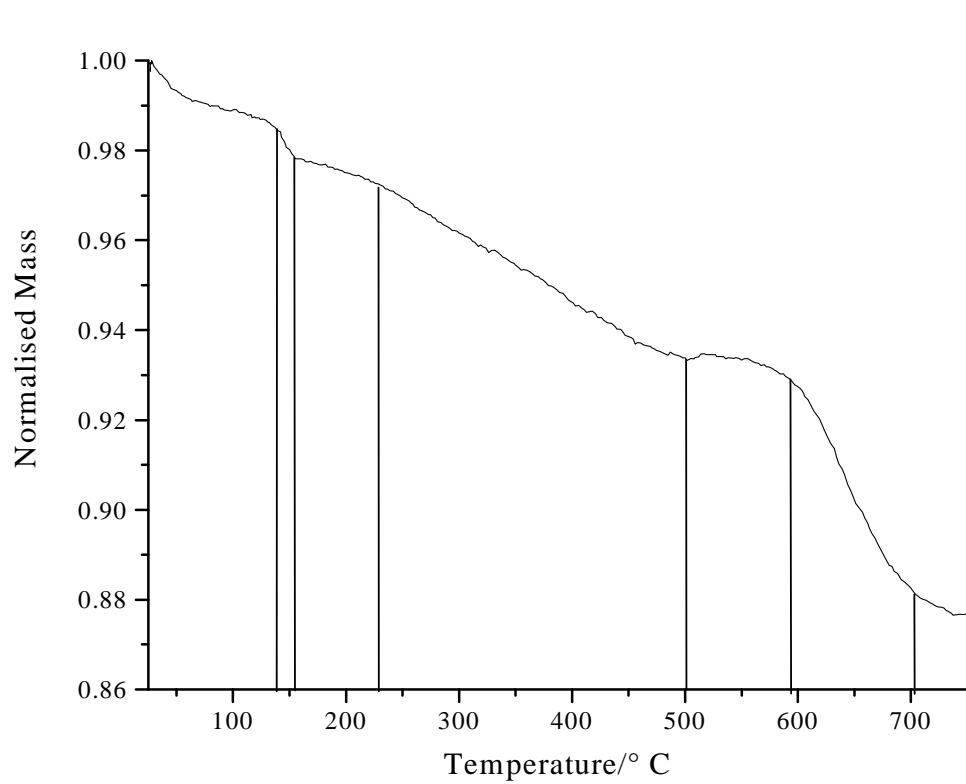

Pore Size/ Ammonia

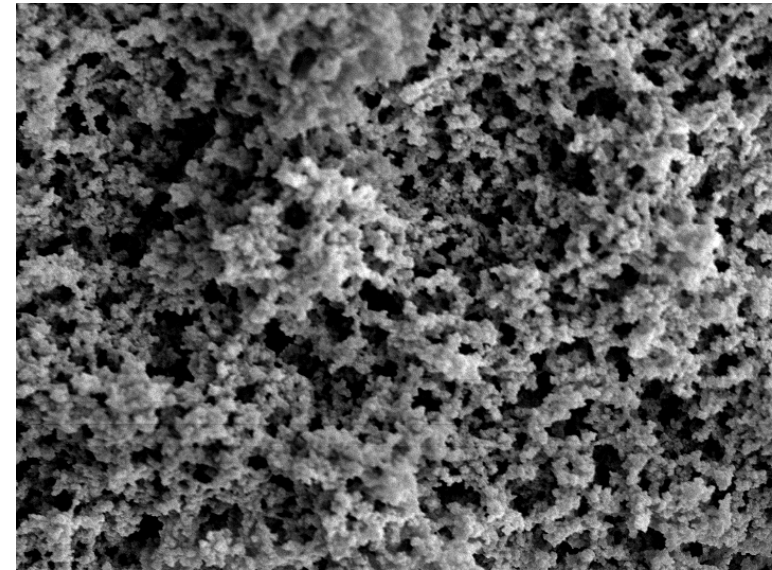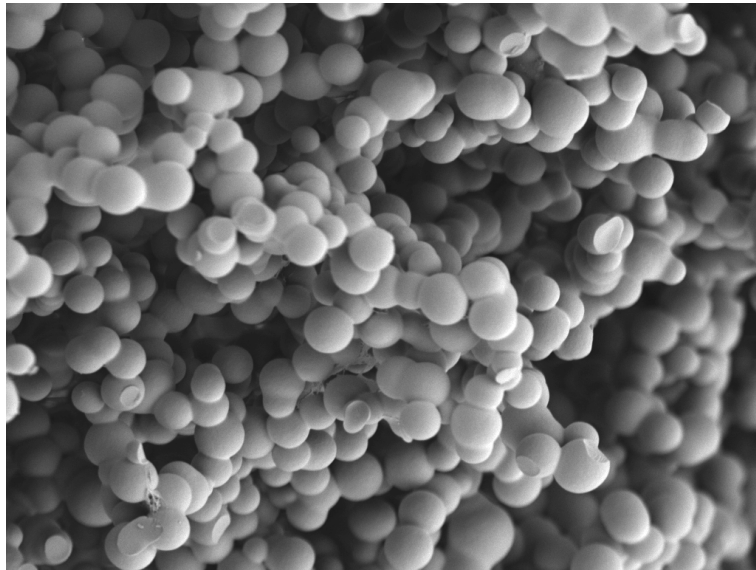


10 μm



MTEOS with 1.1 M ammonia, heated to 300° C

MTEOS with 2.2 M ammonia, heated to 300° C





Contact Angle/ Ammonia

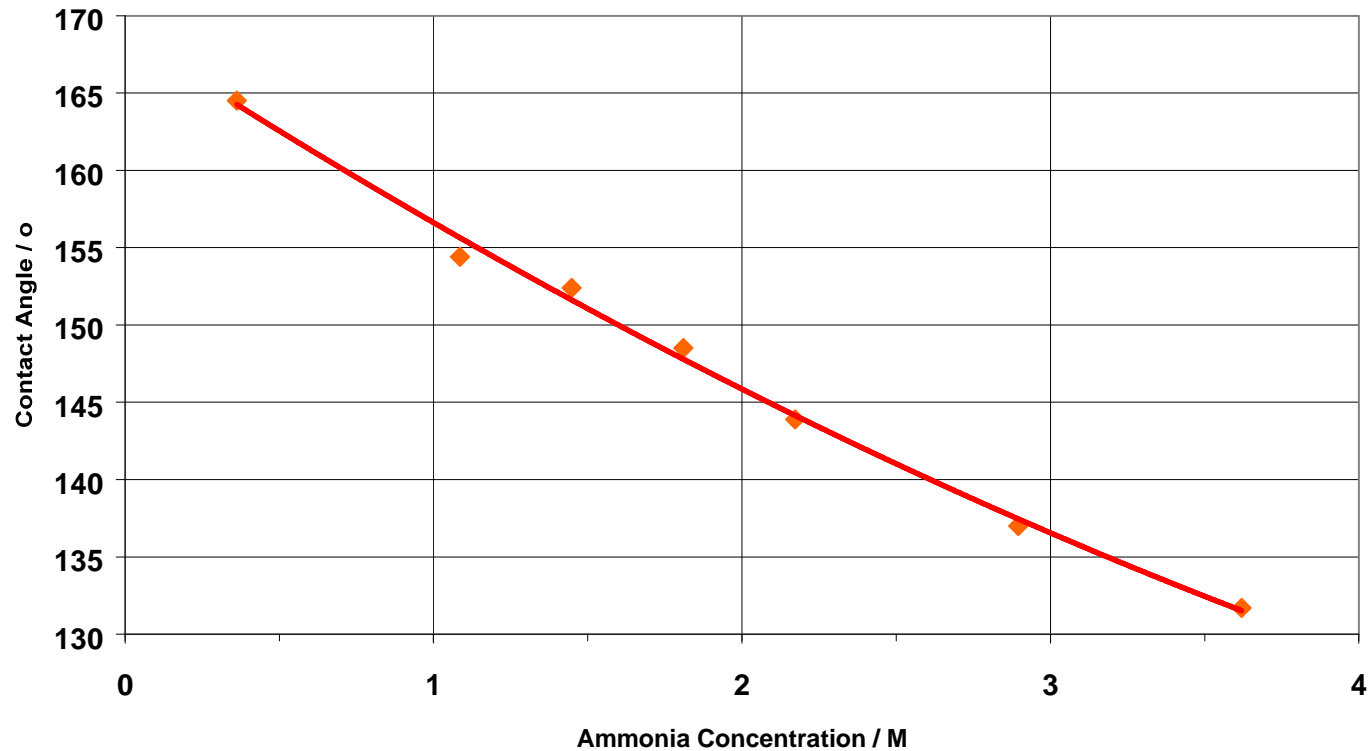

Pore Size/End Group

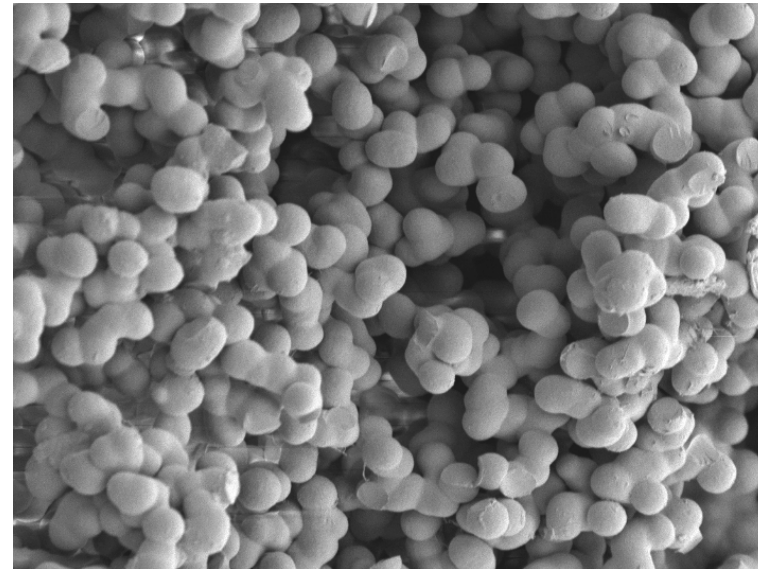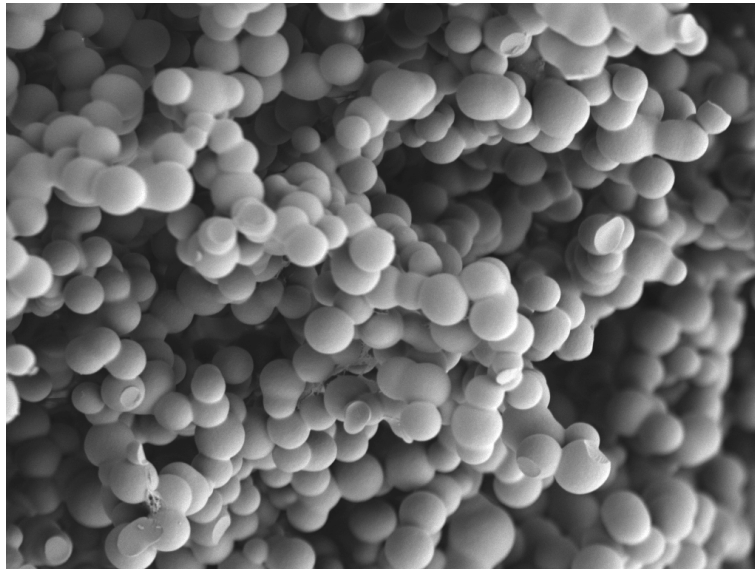

MTEOS with 1.1 M ammonia, heated to 300°C PTEOS with 22 M ammonia, heated to 300°C

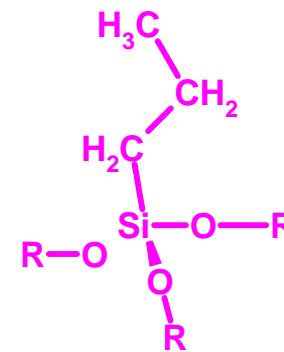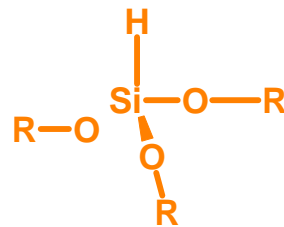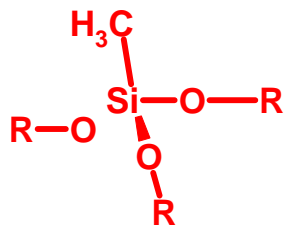

Sol-Gel Films




Properties

Thermally insulating


Waterproof or water absorbing

Gas permeable


Useful thickness depends on pore size

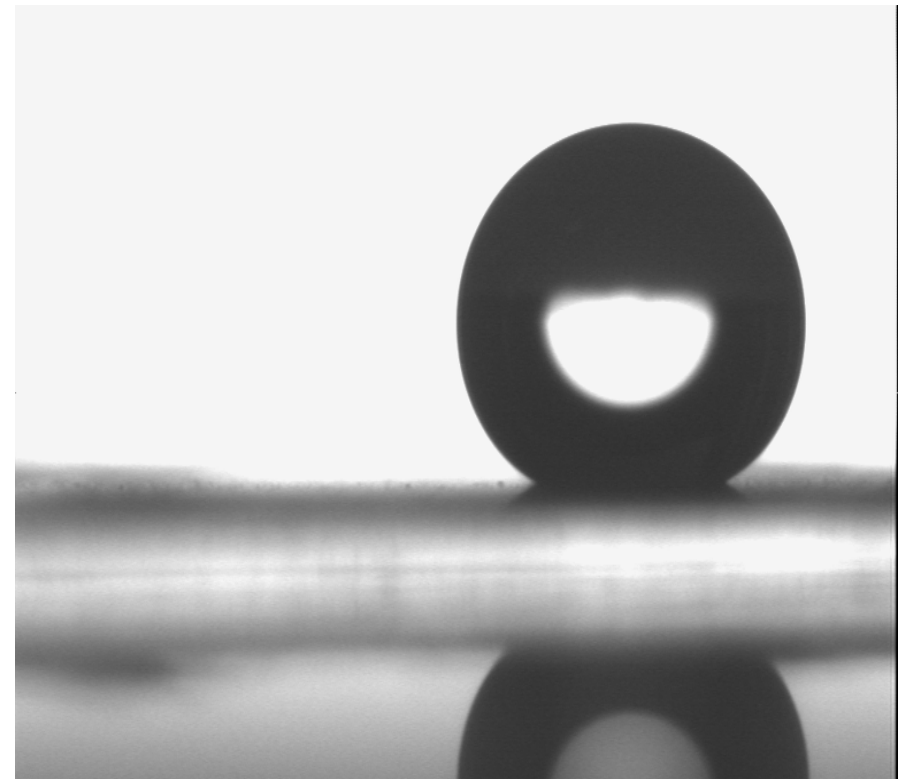




Recipe




DMF

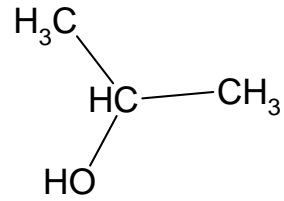



IPA

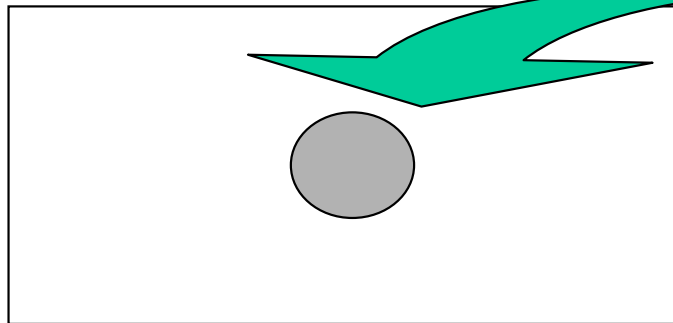

Water Contact Angle / Hydrolysis Time

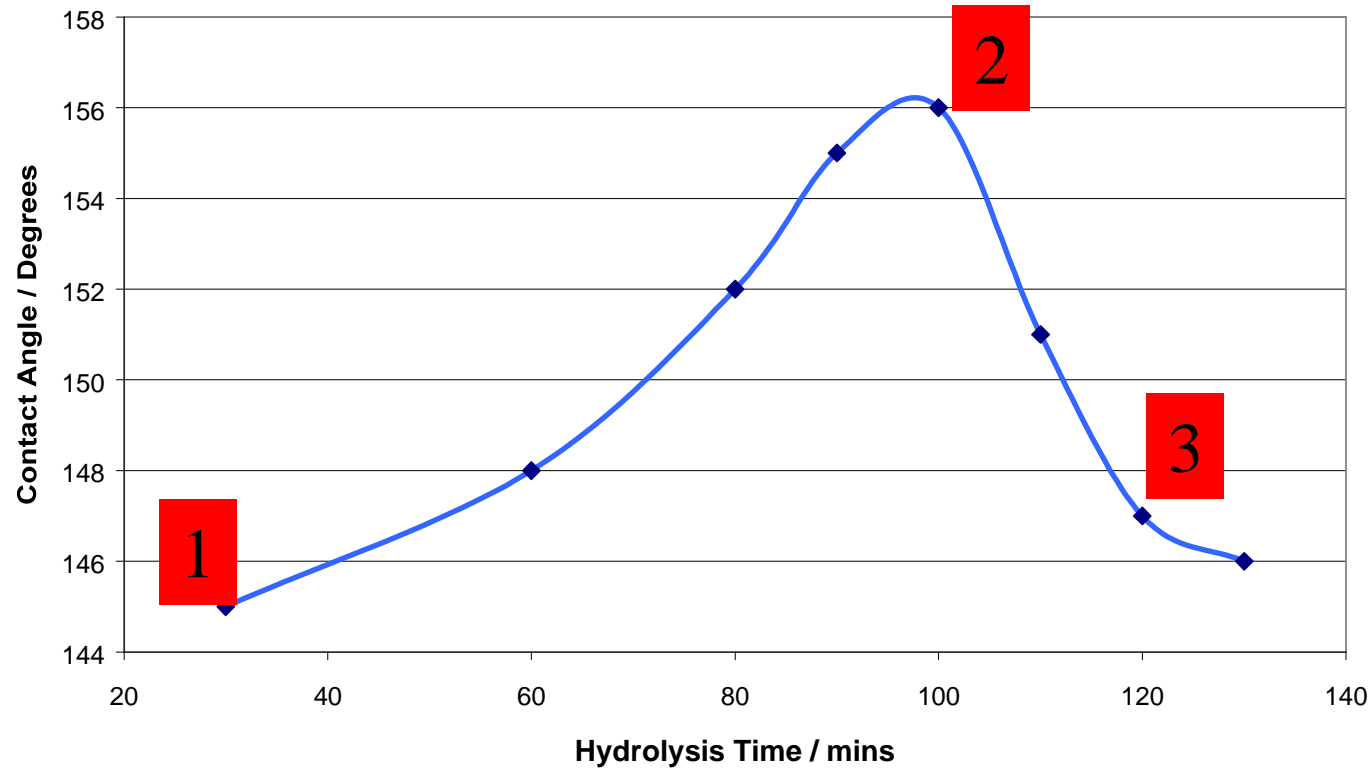

Thin Films Look Like Trees

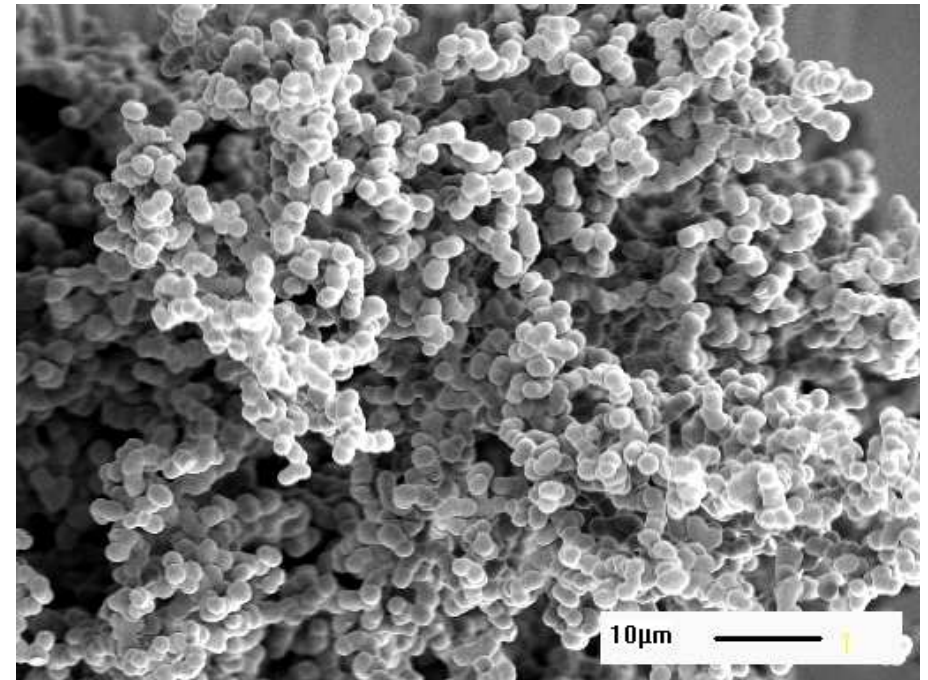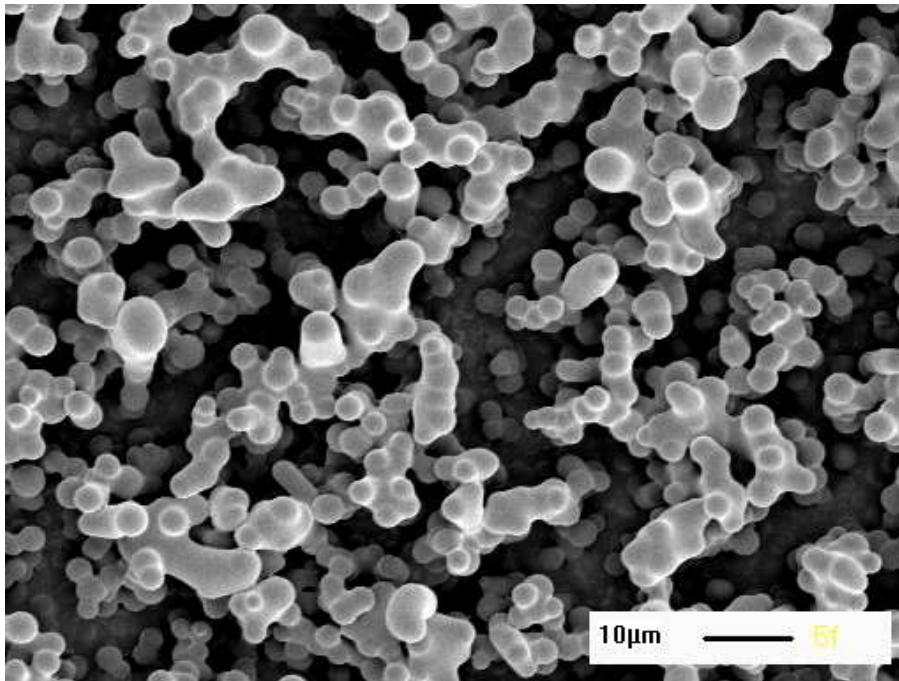

and have lower contact angles

Conclusion



- Can produce layers of sol-gel that are very hydrophobic and porous.
- Can vary pore size using hydrolysis time, solvent polarity and monomer
- Can vary hydrophobicity by thermal treatment
- With supercritical drying, will be attempting to decouple pore size and pore fraction
- With suitable coupling agents have coated glass and gold